

UNIFIED FACILITIES CRITERIA (UFC)

RUNWAY AND ROAD DESIGN: ARTIC AND SUBARCTIC CONSTRUCTION



APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED

UNIFIED FACILITIES CRITERIA (UFC)

RUNWAY AND ROAD DESIGN: ARTIC AND SUBARCTIC CONSTRUCTION

Any copyrighted material included in this UFC is identified at its point of use. Use of the copyrighted material apart from this UFC must have the permission of the copyright holder.

U.S. ARMY CORPS OF ENGINEERS (Preparing Activity)

NAVAL FACILITIES ENGINEERING COMMAND

AIR FORCE CIVIL ENGINEER SUPPORT AGENCY

Record of Changes (changes are indicated by \1\ ... /1/)

Change No.	Date	Location

This UFC supersedes TM 5-852-3, dated 29 October 1954. The format of this UFC does not conform to UFC 1-300-01; however, the format will be adjusted to conform at the next revision. The body of this UFC is the previous TM 5-852-3, dated 29 October 1954.

FOREWORD

v\

The Unified Facilities Criteria (UFC) system is prescribed by MIL-STD 3007 and provides planning, design, construction, sustainment, restoration, and modernization criteria, and applies to the Military Departments, the Defense Agencies, and the DoD Field Activities in accordance with [USD\(AT&L\) Memorandum](#) dated 29 May 2002. UFC will be used for all DoD projects and work for other customers where appropriate. All construction outside of the United States is also governed by Status of forces Agreements (SOFA), Host Nation Funded Construction Agreements (HNFA), and in some instances, Bilateral Infrastructure Agreements (BIA.) Therefore, the acquisition team must ensure compliance with the more stringent of the UFC, the SOFA, the HNFA, and the BIA, as applicable.

UFC are living documents and will be periodically reviewed, updated, and made available to users as part of the Services' responsibility for providing technical criteria for military construction. Headquarters, U.S. Army Corps of Engineers (HQUSACE), Naval Facilities Engineering Command (NAVFAC), and Air Force Civil Engineer Support Agency (AFCESA) are responsible for administration of the UFC system. Defense agencies should contact the preparing service for document interpretation and improvements. Technical content of UFC is the responsibility of the cognizant DoD working group. Recommended changes with supporting rationale should be sent to the respective service proponent office by the following electronic form: [Criteria Change Request \(CCR\)](#). The form is also accessible from the Internet sites listed below.

UFC are effective upon issuance and are distributed only in electronic media from the following source:

- Whole Building Design Guide web site <http://dod.wbdg.org/>.

Hard copies of UFC printed from electronic media should be checked against the current electronic version prior to use to ensure that they are current.


AUTHORIZED BY:



DONALD L. BASHAM, P.E.
Chief, Engineering and Construction
U.S. Army Corps of Engineers



DR. JAMES W. WRIGHT, P.E.
Chief Engineer
Naval Facilities Engineering Command



KATHLEEN I. FERGUSON, P.E.
The Deputy Civil Engineer
DCS/Installations & Logistics
Department of the Air Force



Dr. GET W. MOY, P.E.
Director, Installations Requirements and
Management
Office of the Deputy Under Secretary of Defense
(Installations and Environment)

DEPARTMENT OF THE ARMY TECHNICAL MANUAL

ARCTIC AND SUBARCTIC CONSTRUCTION

RUNWAY AND ROAD DESIGN

This copy is a reprint of former Engineering Manual part XV, Chapter 3.
Redesignated TM 5-852-3 By DA Cir 310-28, 17 March 1965.

HEADQUARTERS, DEPARTMENT OF THE ARMY
OCTOBER 1954

HEADQUARTERS
DEPARTMENT OF THE ARMY
WASHINGTON, D.C., 29 October 1954

TM 5-8523, is published for the use of all concerned.

By Order of the Secretary of the Army:

Official:
JOHN A. KLIEN
Major General, United States Army
The Adjutant General

MATTHEW B. RIDGWAY
General, United States Army
Chief of Staff

**CHAPTER 3
RUNWAY AND ROAD DESIGN**

- 3-01 GENERAL
 - a. Effect of subgrade soil conditions on design
 - b. Effect of frost and permafrost conditions
 - c. Effect of ground water
- 3-02 BASE COURSE AND PAVENMENT COMIPOSITION
 - a. Recommendations for base courses
 - b. Recommendations for pavements
- 3-03 BASE COURSE DESIGN IN AREAS OF NON-FROST-SUSCEPTIBLE SOILS
- 3-04 BASE COURSE DESIGN IN AREAS OF FROST-SUSCEPTIBLE SUBGRADES
 - a. Design to restrict seasonal thaw to pavement and base depth
 - b. Design based on reduced strength of subgrade
- 3-05 BASE COURSE DESIGN IN AREAS OF HIGHLY ORGANIC SOILS
- 3-06 EXAMPLES OF PAVEMENT DESIGN
 - a. Example 1
 - b. Example 2
- 3-07 DRAINAGE
- 3-08 CORDUROY ROADS

Part XV
ARCTIC AND SUBARCTIC CONSTRUCTION
CHAPTER 3
RUNWAY AND ROAD DESIGN

3-01. GENERAL. The construction of satisfactory roads and runways in permafrost areas is normally more difficult than in temperate regions because the imperviousness of the underlying permafrost tends to produce poor soil drainage conditions, and because disturbance of the natural surface may set in motion adjustments in thermal regime, drainage, and slope stability which may have serious and progressive consequences. Cuts should be avoided if possible, and side slopes in fill composed of fine-grained materials should be kept to a 4 to 1 ratio or flatter.

a. Effect of subgrade soil conditions on design. The design of pavement sections is very dependent upon the type of subgrade soils. Clean coarse-textured soils are subject to negligible heaving when frozen, and to only nominal consolidation when thawed. Permafrost in such soil deposits is normally homogeneous and normally contains no segregated ice. Design problems are simplified with such soils, as frost conditions do not alter their stability or bearing capacity.

The danger of loss in bearing capacity upon thawing, and of heaving action upon freezing, is greatest in fine-textured soils. Such action in a soil is dependent upon the availability of water, and to a large degree on void sizes, and may be expressed as an empirical function of grain size, as follows:

Inorganic soils containing 3 percent or more of grains finer than 0.02 mm. in diameter by weight are generally frost-susceptible. Although uniform sandy soils may have as high as 10 percent of grains finer than 0.02 mm. by weight without being frost-susceptible, their tendency to occur interbedded with other soils makes it generally impractical to consider them separately.

Soils in which ice segregation generally occurs when favorable ground water and freezing temperatures are present have been classified in the following four groups, listed approximately in the order of increasing susceptibility to frost heaving and/or weakening as a result of frost melting. The order of listing of subgroups *under* groups F3 and F4 does not necessarily indicate the order of susceptibility to frost heaving or weakening of these subgroups. There is some overlapping of frost susceptibility between groups. The soils in group F4 are of especially high frost susceptibility. Soil names are as defined in the Unified Soil Classification System.

<i>Group</i>	<i>Description</i>
F1	Gravelly soils containing between 3 to 20 percent finer than 0.02 mm. by weight.
F2	Sands containing between 3 and 15 percent finer than 0.02 mm. by weight.
F3	(a) Gravelly soils containing more than 20 percent finer than 0.02 mm. by weight. (b) Sands, except very fine silty sands, containing more than 15 percent finer than 0.02 mm. by weight. (c) Clays with plasticity indexes of more than 12. (d) Varved clays existing with uniform subgrade conditions.
F4	(a) All silts including sandy silts. (b) Very fine silty sands containing more than 15 percent finer than 0.02 mm. by weight. (c) Clays with plasticity indexes of less than 12. (d) Varved clays existing with nonuniform subgrade conditions.

Varved clays consist of alternate layers of inorganic silts and clays and in some instances fine sand. The thickness of the layers rarely exceeds one-half inch, but occasionally very much thicker varves are encountered. They are likely to combine the undesirable properties of both silts and soft clays. Varved clays are likely to soften more readily than homogeneous clays with equal average water contents. However, local experience and conditions should be taken into account, since under favorable conditions, as when insufficient moisture is available for significant ice segregation, there

may be little or no detrimental frost action. There is some evidence that pavements constructed on varved clay subgrades, subject to freezing, in which tile deposit and depth to ground water are relatively uniform, I have performed satisfactorily. When subgrade conditions are uniform and there is local evidence that the degree of heave is not exceptional the varved clay subgrade soil should be assigned a group F3 frost susceptibility classification.

Road and runway design over frost-susceptible soils must take into account frost and permafrost conditions. Soils information should be obtained from borings and test pits to at least the depths indicated for the final stage of site selection as described in chapter 2. The number of holes or pits required can only be determined from physical conditions and the experience of the engineer.

b. *Effect of frost and permafrost conditions.* Frost and permafrost conditions may be altered by changed surface conditions produced by construction. Such challenges have a considerable effect on the stability of roads and runways and must be considered in their design. Depths of freeze and thaw before and after construction may differ considerably. Figure 1 illustrates the effect of clearing and stripping on the depth to the permafrost table after a period of 5 years. Figure 2 shows an idealized sketch of the maximum thaw beneath a road and adjoining areas where thaw is caused by surface heat and the effect of running water in road ditches. The surface temperature for a given air temperature is strongly affected by a considerable variety of factors, and the mean annual surface temperature may differ considerably from that of the air. The effect of surface type on depth of thaw is illustrated by table 1.

The change of the level of the permafrost table after construction should be considered in design. Construction may result in a degradation of the permafrost (a condition resulting if annual thaw exceeds annual freeze) or in a condition where thaw and annual freeze penetrate into soil which has previously existed as permafrost. Degradation of permafrost in cuts may lead to slides or sloughing, often difficult to stabilize. Where degradation is anticipated, soils should be investigated to a depth sufficient to determine the eventual effects of such progressive action. The depth of thaw and of freeze which will occur after construction may be calculated by methods given in chapter 6

Thawing of previously unthawed subgrades which have a high ice content, such as with thick closely spaced ice lenses, buried ice masses, or ice-filled polygon fissures will result in serious and

Table 1 - Measured Depth of Thaw Below Various Surfaces in the Subarctic After 5 Years.. (Fairbanks, Alaska, Mean Annual Temperature 26° F.)

Type of surface	Color of surface	Thickness of pavement in feet	Nature of base course	Thickness of base course in feet	Approximate elevation of water table	Observed total depth of thaw in feet	Depth of thaw in feet into silt subgrade
Gravel.....	Natural.....		Sand and gravel.	4.0	Bottom of base course.	8.0 - 10.5	4.0 - 6.5
Concrete.....	Natural.....	0.5	Sand and gravel	4.0	Bottom of base course.	8.5 - 9.5	4.0 - 5.0
Concrete.....	Natural.....	0.5	Sand.....	4.0	Bottom of base course.	8.5 - 9.5	4.0 - 5.0
Asphalt.....	Black.....	0.4	Sand and gravel.	4.0	Bottom of base course.	8.5 - 10.0	4.0 - 5.5
Trees, brush, grass, and moss	Natural vegetation.-				Surface.....	3.0 - 4.0	3.0 - 4.0
Grass and moss	Natural minus trees and brush.				Surface.....	5.0 - 6.0	5.0 - 6.0
Grass without moss	Natural grass				Surface.....	8.0 - 9.0	8.0 - 9.0

abrupt surface subsidence. Thawing of such subgrades beneath completed pavements should be prevented by providing sufficient base-course thickness, or the effects of thawing should be anticipated in planning future maintenance requirements. Stage construction, where possible, such as for roads, should be considered so that final high-type surfacing is placed after completion of the greater portion of subsidence due to thawing.

Where pavement construction is not going to result in a degrading condition, there may be advantage in placing the base course directly on the existing vegetative cover as described in paragraph 1-04e(1), chapter 1, of this part. The settlement due to compressibility of surface materials, and movement due to seasonal freezing and thawing of surface cover deposit, and soils in the active zone prior to construction will generally be much less serious than thawing of previously unthawed subgrade soils containing considerable segregated ice.

c. *Effect of ground water.* In areas of permafrost the location of the ground water surface is greatly influenced by the existence of the underlying impervious permafrost layer. Surface infiltration and water released by the melting of frozen soil supply water to the thawed zone above the permafrost layer during the summer period. Unless the soil is relatively pervious and the terrain has sufficient slope to permit lateral drainage, the water table may rise to, or near, the ground surface. During the early part of the freezing period lack of precipitation, cessation of thawing of the permafrost layer, and reduction in infiltration by freezing of the ground surface combine to restrict the entrance of water to the seasonally thawed layer. Where the terrain is sloping and the soil relatively pervious (coefficient of permeability greater than approximately 1×10^{-4} ft/min), the free water will tend to drain by gravity as freezing temperatures penetrate below the surface, and in addition water is drawn to the zone of freezing in frost-susceptible soils. As a result the ground water surface will approach the upper surface of the permafrost layer. However, where there is a considerable drainage area above a specific location, the water level may remain above the permafrost table for a considerable part of the freezing season, due to the time-lag in the subsurface flow, and in addition to supplying water for ice segregation in the active zone, may cause the formation of surface icings and/or frost mounds.

In evaluating probable ground water conditions during the freezing period at a particular site, observations and consideration of topographic position, slope of terrain, vegetative cover, and the soil type should be utilized. A potentially troublesome water supply for ice segregation is present if the uppermost ground water surface is within 5 feet of the plane of freezing, while if the ground water depth is in excess of 10 feet, appreciable ice segregation usually will not occur. However, fine-grained, frost-susceptible subgrade soils in permafrost regions will usually become sufficiently saturated to result in some ice segregation, even when the water table is remote. This applies to soils in groups CL, CH, OL, OH, MH and to a lesser extent ML. In such cases, the total depth of the thawed layer as well as the degree of saturation will influence the amount of ice segregation. Significant ice segregation will generally not occur in frost-susceptible soils with a remote water table, when the degree of saturation is less than approximately 70 percent.

Where water for ice segregation is extracted from the voids of the soil below the zone of freezing, the surface heaving generally will not be objectionable. When a frost-susceptible soil of group F3 or F4 is at or near full saturation, the movement of water from the bottom to the top of the soil layer during the freezing process will tend to result in weakening the soil at time of frost melting. In such cases the *minimum* base-course thickness should be determined by use of *reduced strength of subgrade method* outlined in paragraph 3-04b.

3-02. BASE COURSE AND PAVEMENT COMPOSITION.

a. *Recommendations for base courses.* All base-course materials lying within the depth of frost penetration should be non-frost-susceptible. Where the combined thickness of pavement and base over a frost-susceptible subgrade is less than the depth of seasonal freeze or thaw, the following additional design requirements apply:

(1) For both flexible and rigid pavements a minimum of 4 inches of base between the subgrade soil and overlying base-course material should be designed as a filter consisting of any non-frost-susceptible gravel, sand, or crushed stone. The gradation of this filter material should be determined in accordance with criteria presented in paragraph 2-11 of chapter 2, part XIII, of the Engineering Manual, with the added overriding limitation that the filter material should in no case have more than 3 percent by weight finer than 0.02 mm. Non-frost-susceptible sand is considered especially suitable for this filter course.

(2) For rigid pavements a filter should also be placed immediately beneath the pavement. This filter should have a maximum of 85 percent by weight passing the 1/4-inch sieve.

(3) The purpose of the filter courses is to prevent the mixing of the frost-susceptible subgrade with the base during the thaw period, and to prevent loss of support by pumping.

b. Recommendations for pavements. Either flexible or rigid types of pavements may be used in arctic and subarctic regions. Type of pavement (rigid or flexible) constructed for USAF should be in accordance with current USAF policy. Rigid pavements should be used only where favorable subgrade conditions exist, such as over non-frost-susceptible subgrades and possibly uniform subgrade soils from groups F1 and F2. Even with the utmost care in soil investigation, design, and construction, differential movements may occur. Repairs in flexible pavements are simpler and more economical than those in rigid pavements. Hot plant-mix bituminous pavements are adapted for extremely cold climates as they may be constructed under relatively adverse weather conditions. Soft grades of asphalt are recommended for preparing hot-mix types of pavement subject to low temperatures. Asphalt cement grade AP 1 (pen. 120-150) conforming to Federal Specifications SS-A-706b is generally recommended. AP 2 (pen. 100-120) may be used in areas where temperatures are relatively higher and weather may be warm part of the year. Paving operations should be coordinated so that the temperature loss of the mixture during transporting and spreading is kept at a minimum. There is a tendency to over-heat the bituminous material when preparing mixtures in cold weather; this should be avoided as the resultant pavements are brittle and short-lived. The spread mixture should be compacted as rapidly as possible to prevent further loss of temperature and to obtain a dense pavement.

In order to insure satisfactory results, concrete pavements must be protected from freezing during the placement and curing period and must be permitted to gain substantial tensile strength before exposure to very low temperatures, to minimize cracking. High early-strength cement with air entrainment is recommended. Joints should be at much smaller spacing than usual because of exceptional expansion and contraction.

3-03. BASE COURSE DESIGN IN AREAS OF NON-FROST-SUSCEPTIBLE SOILS. In areas where the soils are non-frost-susceptible, or where the soils are frost-susceptible but ground water conditions preclude significant ice segregation, design principles are the same as in temperate zones. Airfield pavements and bases should be designed in accordance with part XII, chapters 2 and 3, (1)* and (2)*; roads should be designed in accordance with part X, chapter 1 (3). If pockets of frost-susceptible-soil exist within the construction area, they should be removed and replaced with non-frost-susceptible materials. The area of excavation of such a pocket should be large enough to allow feather-edging of the backfill; the depth of excavation should be not less than the estimated depth of frost penetration in the backfill material.

3-04. BASE COURSE DESIGN IN AREAS OF FROST-SUSCEPTIBLE SUBGRADES.

Two acceptable methods of design of base courses are available where frost-susceptible soils and frost-susceptible ground water conditions exist. One method is to restrict the depth of seasonal thaw to the pavement and base course, thereby preventing surface subsidence and subgrade weakening. The other method is to allow thawing to penetrate the subgrade and to design on the basis of anticipated reduced strength of the subgrade during the thawing period.

*Refers to bibliographic references listed at end

In order to use the minimum base-course thickness required to restrict the seasonal thaw to pavement and base depth, consideration should be given to using relatively high moisture retaining non-frost-susceptible soils, such as uniform sands in the lower base. After initial freezing such soils provide considerable resistance to thaw penetration because of the high latent heat required to melt them. The use of frost-susceptible soils of groups F1 and F2 in the lower base is also permissible if some heaving may be tolerated and these soils are covered with a thickness of non-frost-susceptible base determined by use of the *reduced strength of subgrade method*. The depth of thaw penetration into such a layered base may be estimated by methods presented in chapter 6. For pavements of lesser importance where considerable heaving is allowable, the use of a group F3 or F4 soil in the lower base is permissible in extreme instances where more suitable materials are not available to prevent initial thawing of a high ice content subgrade with large ice concentration. In such cases, the minimum thickness of the non-frost-susceptible base course over group F3 or F4 soils shall be determined by the reduction in strength method and some, possibly objectionable, heaving should be anticipated.

a. *Design to restrict seasonal thaw to pavement and base depth.* In arctic regions a design which will keep the seasonal thaw within the base-course depth will keep the subgrade frozen and prevent frost heaving or damaging surface settling. The required gravel base thickness may be determined from figure 3, utilizing the thawing index of the pavement surface and the 5 percent base moisture content for which the curve is computed, unless information on base materials indicates a different moisture content can be maintained. For base courses at other moisture contents, the thicknesses shown in figure 3 may be multiplied by the appropriate factor given in the note. Observations have shown that a base consisting of non-frost-susceptible material normally has a moisture content between 3 and 6 percent. A completely saturated gravel base will only rarely contain more than 9 percent moisture. The surface thawing index may be computed by multiplying the thawing index based on air temperatures by a correction factor for the type of surface. This correction factor may be taken as 1.6 for bituminous pavements and 1.5 for portland cement concrete pavements. In each individual case the air thawing index should be computed with specific site data; however, order-of-magnitude values may be estimated from figures 6 and 8 in chapter 1.

The thickness determined for figure 3 is the thickness of the non-frost-susceptible base only and is not the combined thickness of pavement and base. Because of the fact that the surface course generally has a very small or negligible moisture content, it follows that little heat is lost in melting the frozen moisture therein. Thus, for determinations of this type, the thermal resistance of surface courses 6 inches thick, or less, may be neglected.

It will be noted from figure 3 that for a base thickness of 6 feet, the surface thawing index must be about 500 or less, to restrict thawing to the gravel base course.

b. *Design based on reduced strength of subgrade.* Since the combined pavement and base thicknesses required to prevent thawing of the subgrade are commonly greater than 6 feet, except in extremely frigid areas, design must usually be based on the assumption that thawing and freezing will occur in the subgrade.

This method may be used for flexible pavements on subgrade soils of groups F1, F2, and F3 and rigid pavements over group F1 and F2 soils, when subgrade conditions are sufficiently uniform to assure that objectional differential heaving or subsidence will not occur, or where subgrade variations are correctible to this condition by removal and replacement of pockets of more highly frost-susceptible or high ice content soils. The method may also be used for design of flexible pavements where appreciable non-uniform heave or subsidence can be tolerated in pavements of lesser importance, used for slow speed traffic, including pavements designed over group F4 subgrades.

When the *reduction in subgrade strength method* is used for design of flexible pavements over subgrade soils of group F4, the combined pavement and base thickness should be determined using design curves for F3 and F4 soils shown on figures 4 through 7. The use of the *reduction in strength method*

for design of rigid pavements should be avoided if at all possible over group F3 soils and particularly over group F4 soils. If special needs or conditions dictate the use of rigid pavements over group F3 and F4 soils, a curve is included on figure 10, so that design can be made.

Use of the *reduction in subgrade strength method* for design of pavements for lightweight highspeed aircraft will give thicknesses adequate to carry traffic, but possibly may result in objectionable surface roughness due to heaving or subsidence. In such cases, design studies should include the compilation of frost heaving and settlement experience records from existing airfield or highway pavements in the vicinity where conditions are comparable. The amount, type, and distribution of ice formation in that portion of the existing frozen soil that will be thawed after pavement construction should be determined and an estimate made of the magnitude and probable unevenness that will result from future subsidence. Based on these design studies, the base-course thicknesses should be increased as necessary, over the thickness obtained by *the reduction in strength method*, to hold the differential surface heave or subsidence to a tolerable amount, or provisions made for resurfacing pavement periodically for a period of years to maintain a level surface. In order to accomplish this, base courses up to 6 feet in thickness may be required to reduce prohibitive differential heaving. Where the subgrade contains large, concentrated, buried ice masses, ice-filled polygon fissures and intense ice lens formations which will be subject to melting after pavement construction, the base thickness should be sufficient to prevent thawing of these ice masses or major maintenance anticipated.

In addition to the conditions stated above, it will be necessary to consider all reliable information concerning performance of airfield and highway pavements constructed in the area being investigated with a view toward modifying or increasing the design requirements. Local experience with soils of a particular frost-susceptible soil group as listed in paragraph 4-04 may indicate that assigning the soils to the next highest or lowest grouping would best conform to actual behavior. Due regard should be given to freezing and ground water conditions in considering local experience with the soils.

(1) *Flexible pavements.* The curves of figures 4, 5, and 6 should be used to determine the combined thickness of flexible pavement and non-frost-susceptible base required for various aircraft wheel loads and wheel assemblies, and figure 7 should be used for highways. These curves reflect the reduction in strength of soil during the frost melting period.

Since design thickness computed by this procedure does not prevent frost heaving, the annual depths of thaw and of freeze should be estimated from figures 8 and 9. (These curves have been developed using the methods presented in chapter 6.) If subsoils are nonuniform or contain pockets of ice, differential surface movements may be expected which can be minimized by removal of such materials. The eventual development of abrupt surface irregularities in the finished pavement may be reduced by the tapering out of all excavations and backfills so as to insure gradual transitions. If annual thaw is greater than freeze, the permafrost will degrade and the depth of thaw may become progressively greater. If the permafrost surface is at some depth beneath the designed pavement section, pockets of highly frost-susceptible soils within the depth of annual freeze should be removed.

In estimating the depth of annual freeze by figure 9, the surface freezing index for bituminous surfaces (kept cleared of snow) may be computed by multiplying the freezing index based on air temperatures by a correction factor of 0.7.

(2) *Rigid pavements* The thickness of concrete pavements should be determined in accordance with chapter 3, part XII, for airfields, and chapter 1, part XIII, for roads, using the subgrade modulus determined from figure 10, which considers the reduced strength of the subgrade in conjunction with the modulus determined in the field. If the tested "k" value is smaller than the subgrade modulus obtained from figure 10, the test value should govern the design.

Where thawing and freezing are permitted in a frost-susceptible subgrade of group F1 or group F2 soil beneath a rigid pavement, the differential movement should generally small.

Consequently, a non-frost-susceptible base course having a minimum thickness equal to that of the concrete slab should be used over these soils. In cases where rigid pavements are constructed over F3 soils, a non-frost-susceptible base course equal to a minimum of one and one-half times the concrete slab thickness should be used. In areas where a frost-susceptible subgrade soil of group F4 is present, appreciable total and differential movement may generally be expected.

Therefore, a non-frost-susceptible base course of a thickness equal to one-half the depth of the subgrade that will be subject to freezing and thawing should be used over F4 soils. In the application of this criterion the computed depth of freeze or thaw, whichever is less, will govern the depth of base course to be employed. In no case should the base-course thickness over an F4 soil be less than 24 inches nor greater than 48 inches.

The annual depths of thaw and freeze can be estimated by use of figures 8 and 9. The depths read from these curves can be considered as depths below the top of the subgrade. In calculations of depth of freeze, correction factor for portland cement concrete (kept clear of snow) may be taken as 0.6. If isolated pockets of ice or highly frost-susceptible materials exist to these depths of thaw and freeze, they should be replaced to minimize differential surface movements.

3-05. BASE COURSE DESIGN IN AREAS OF HIGHLY ORGANIC SOILS. Every effort should be made to avoid construction on organic soils. However, because of the existence of extensive peat bogs and muskeg in the Arctic and Subarctic, it is occasionally necessary to construct roads on such areas because of the lack of an alternate route. In this case a thorough soil survey should be made to determine the depth and extent of the soft sediments in order that the best possible route may be determined. From field experience it is considered that in bogs having a surficial peat deposit less than 5 feet thick the peat should be removed and replaced with granular fill: in deep peat bogs fill may be placed directly on the undisturbed cover. In either case the fill should be at least 5 feet thick regardless of surfacing and, in the latter instance, it may be found that great quantities of fill may be necessary as the underlying organic material is compressed or forced out to the sides. In any event continued differential settlement and almost constant maintenance may be expected.

3-06. EXAMPLES OF PAVEMENT DESIGN.

a. *Example.*

Design an airfield taxiway for both flexible and rigid pavements to withstand a 40,000 pound single wheel load with 100 psi tire pressure, for the following conditions:

Mean air thawing index, 3000 degree days (F)

Mean air freezing index, 5500 degree days (F)

Subgrade = silt. 60 percent by weight of grains finer than 0.02 mm., moisture content = 45 percent group F4

Subgrade modulus, k (test made on top of gravel base) 300 lb./sq. in./in.

Base CBR = 80 percent

Concrete flexural strength = 650 lb./sq. in.

(1) *Flexible pavement.*

(a) *Design to restrict annual thaw to pavement and base depth..*

Surface thawing index = (air thawing index) x (correction factor)

$$= 3000 \times 1.6 = 4800 \text{ degree days (F)}$$

From figure 3, for 5 percent moisture content, the depth of gravel base required is greater than 160 inches. This is an impractical value, and therefore this design is not applicable.

(b) *Design based on reduced strength of subgrade.* According to figure 4, for an F4 soil, 36 inches of pavement and base is required. The section may be a 4-inch bituminous wearing course plus a 32-inch gravel base. (See paragraph 2-18, chapter 2, part XII for bituminous

pavement thickness requirements.) The lower portion of the base (at least 4 inches) should be designed as a filter.

$$\begin{aligned} \text{Surface freezing index} &= (\text{air freezing index}) \times (\text{correction factor}) \\ &= 5500 \times (0.7) \\ &= 3850 \text{ degree days (F)} \end{aligned}$$

By figure 9, for 24-in. base, depth of freeze below base = 58 in.

By figure 9, for 48-in. base, depth of freeze below base = 45 in.

Interpolating for 32-in. base depth of freeze below

$$\text{base} = 58 - \frac{32 - 24}{48 - 24} (58 - 45) = 54 \text{ in.}$$

Depth of thaw:

Surface thawing index = 4800 degree days (F)

By figure 8, for 24-in. base, depth of thaw below base = 52 in.

By figure 8, for 48-in. base, depth of thaw below base = 44 in.

$$\text{Interpolating, for 32-in. base } 52 = \frac{32 - 24}{48 - 24} (52 - 44) = 49 \text{ in.}$$

This would indicate that the permafrost probably would not degrade, since the depth of freeze is, by computation, 5 inches greater than the depth of thaw.

The soils should be investigated to a depth of at least 4 feet beneath the proposed subgrade elevation for nonuniformity and isolated pockets of high frost-susceptibility.

(2) *Rigid pavement.* Although the use of rigid pavements is not recommended over an F4 soil, assume for the purpose of this example that special conditions dictate its use.

(a) *Design to restrict annual thaw to pavement and base depth.* It would be impractical to design a base depth to keep the subgrade from thawing, as was shown for the flexible pavement.

(b) *Design based on reduced strength of subgrade.* A base thickness equal to one-half the depth of the subgrade that will be subject to freezing and thawing is required. In no case should the base thickness be less than 24 inches nor greater than 48 inches.

Surface freezing index = 3850 degree days (F)

By figure 9, for 24-in. base, depth of freeze below base = 58 in.

By figure 9, for 48-in. base, depth of freeze below base = 45 in.

Depth of thaw:

Surface thawing index = 4800 degree days (F)

By figure 8, for 24-in. base, depth of thaw below base = 52 in.

By figure 8, for 48-in. base, depth of thaw below base = 44 in.

From the above, with a depth of thaw for the minimum base thickness (24 inches) less than the depth of freeze for that thickness, it is evident that only 52 inches of subgrade is subjected to annual freeze and thaw. Therefore, a base thickness one-half the depth of thaw or 26 inches would be used. At least 4 inches of the lower portion of this base should be designed as a filter.

The slab thickness may be determined by use of figure 10 and the pavement design curves in part XII, chapter 3. By figure 10, a subgrade modulus of 150 lbs. per sq. in. per in. is obtained. By the curve of part XII, chapter 3 a slab thickness of 11 inches is obtained.

b. *Example 2.*

Design an airfield taxiway for both flexible and rigid pavements, to withstand a 100,000 pound dual wheel load, contact area each wheel 267 sq. in., for the following conditions:

Mean air thawing index, 300 degree days (F)

Mean air freezing index, 9000 degree days (F)

Subgrade = silty sand, 10 percent by weight of grains finer than 0.02 mm., moisture content=25 percent group

F2 Subgrade modulus, k (test made on top of gravel base) =300 lbs./sq. in./in.

Base CBR=80 percent

Base moisture content expected=3 percent
Concrete flexural strength=650 lbs./sq. in.

(1) *Flexible pavement.*

(a) *Design to restrict annual thaw to pavement and base depth.*

Surface thawing index= (air thawing index) x (correction factor,
=300 x 1.6=480 degree days (F)

Depth of gravel base required, from figure 3, for 3 percent moisture content in
base=70 x 1.19=83 in.

For the reason explained in paragraph 3-04a, the thickness of the bituminous surface is not included in the thickness computed above.

(b) *Design based on reduced strength of subgrade.* Subgrade is an F2 soil. By figure 5, 36 inches combined thickness of pavement and base is required. If the bituminous surface is 4 inches thick, base thickness is 32 inches. The lower 4 inches of the base should be designed as a filter.

The depth of annual thaw may be approximate by interpolation in figure 8. For a surface thawing index of 480, depth of annual thaw into subgrade= 11 inches. At least this depth in the subgrade should be investigated for non-uniformity and pockets of highly frost-susceptible soils.

Such soils and pockets of clear ice should be removed to avoid excessive surface heaving or settlements.

By figure 9, it can be ascertained that the annual freeze is considerably greater than the annual thaw. Thus there will be no degradation of the permafrost below the new depth of annual thaw.

(2) *Rigid pavement.*

(a) *Design to restrict annual thaw to pavement and base depth.* By use of figure 3 and a surface thawing index of 450 degree days F, (300 x 1.5), a base thickness of 81 inches is required to prevent subgrade thawing. This method neglects the thermal resistance of the pavement which, in the case of thick concrete slabs, may be significant. Using formula (6) in chapter 6 and an assumed slab thickness of 15 inches, the estimate base course thickness to prevent subgrade thaw is 67 inches.

(b) *Design based on reduced strength of subgrade.* By design curves for concrete pavements for dual wheels in part XII, chapter 3, a first trial slab thickness of 15 inches is obtained.

With this a 15-inch base course would be required. By figure 10, the reduced subgrade modulus, k , with a 15-inch base is 120 lbs. per sq. in. per in. Using this value for k in the design curve for slab thickness, a new value of 17 inches for slab thickness is obtained. The base course should, therefore, also be 17 inches. The k value of 130 from figure 10 for a 17-inch base does not change the thickness of the concrete slab. The lower 4 inches of this base should be designed as a filter. The depth of thaw for a 17-inch base thickness, by interpolation in figure 8, is 16 inches in the subgrade. Investigation of the soils for at least this depth should be made so that undesirable pockets can be eliminated. The depth of freeze from figure 9 would be more than 100 inches, which indicates that there will be no permafrost degradation.

3-07. DRAINAGE. Drainage ditches should be deep and narrow to minimize surface area.

They should preferably be lined to prevent seepage, which would increase the depth of thaw, and erosion, which might cause blockage and ponding. Ponding must be avoided as it causes icing.

Frequent culverts of double the normal capacity are valuable; subdrains are of little use, however.


A steam pipe should be installed in every culvert to permit artificial thawing.

3-08. CORDUROY ROADS. Where standing timber is available, corduroy may be used for temporary roads and sometimes in permanent roads over poor soils if a better material is unobtainable. Corduroy must be protected by a sand, gravel, or stone cover.


BIBLIOGRAPHY

- (1) Corps of Engineers (1951). Engineering Manual for Military Construction, part XII, chapter 2, Airfield Pavement Design, Flexible Pavements.
- (2) Corps of Engineers (1951). Engineering Manual for Military Construction, part XII, chapter 3, Airfield Pavement Design, Rigid Pavements.
- (3) Corps of Engineers (1947). Engineering Manual for Military Construction, part X, chapter 1, Transportation Facilities, Roads, Walks and Open Storage Areas.
- (4) Corps of Engineers (1950). Investigation of Airfield Drainage in Arctic and Subarctic Regions, (Restricted). Two volumes, Prepared by the University of Minnesota for Permafrost Division,* St. Paul District.
- (5) Department of the Army (1950). Construction of Runways, Roads and Buildings on Permanently Frozen Ground, TB5-255-3, Washington, D. C.
- (6) Corps of Engineers (1950), Comprehensive Report, Investigation of Military Construction in Arctic and Subarctic Regions, 1945-1948 (Restricted). Main report and three appendices: Appendix 1-Airfield Site Studies of Northway Airfield, Alaska; Appendix 2-Library Research; Appendix 3-Design and Construction Studies at Fairbanks Research Area, St. Paul District.

*Functions of the former Permafrost Division are now incorporated in the Arctic Construction and Frost Effects Laboratory, New England Division, Boston, Mass

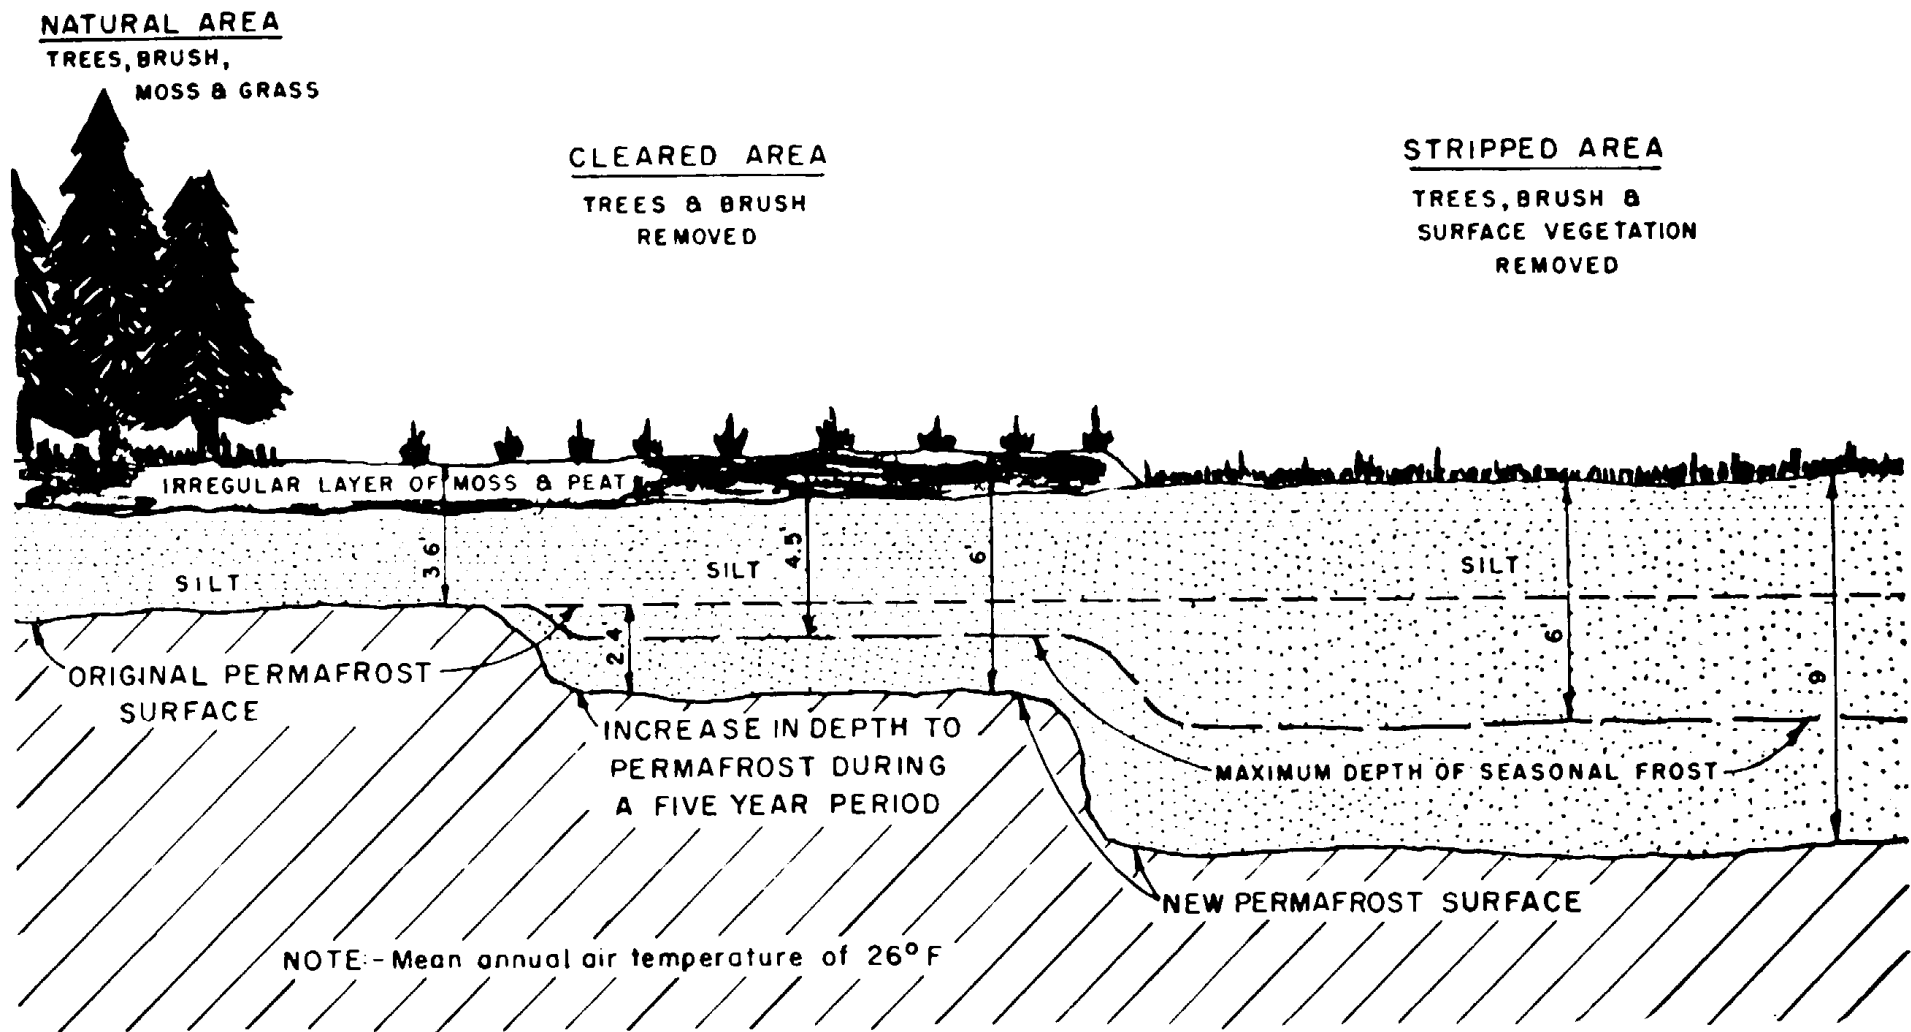

MEASURED DEGRADATION OF PERMAFROST IN FROST-SUSCEPTIBLE SOILS
BELOW DIFFERENT SURFACES IN A SUBARCTIC REGION
AFTER A FIVE YEAR PERIOD

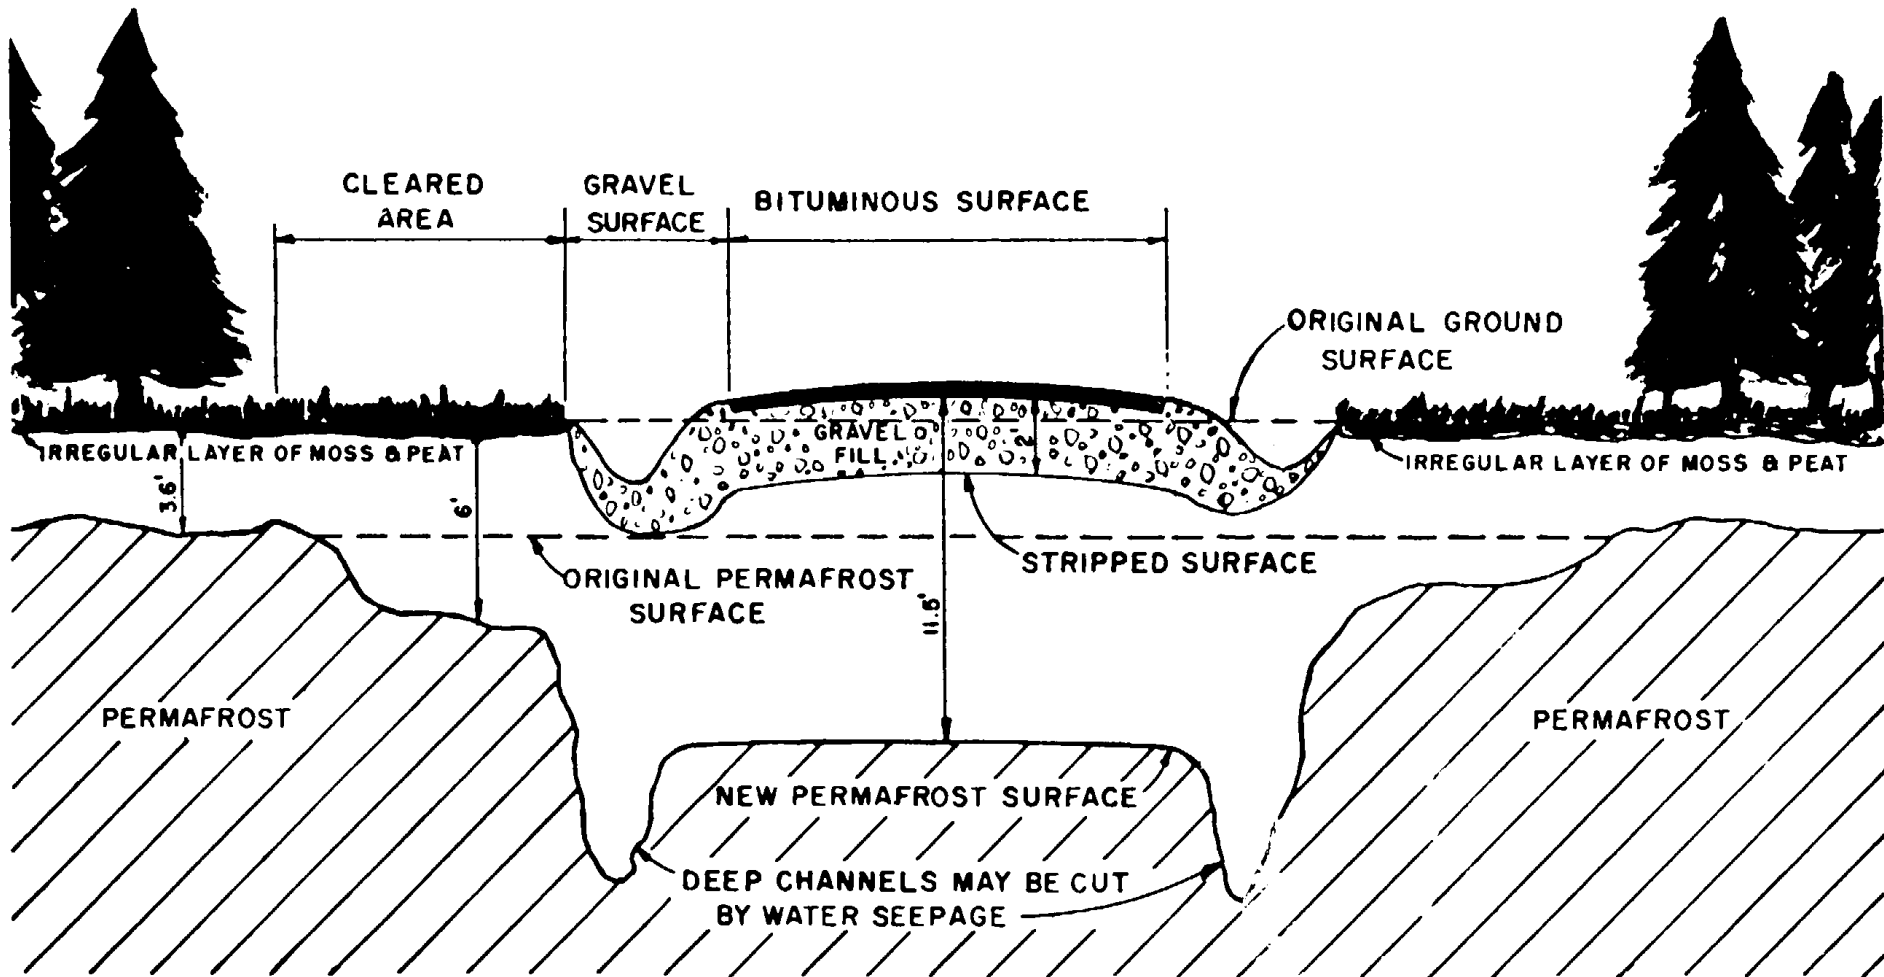

**MAXIMUM DEPTH TO PERMAFROST BELOW A ROAD AFTER FIVE YEARS
IN A SUBARCTIC REGION**


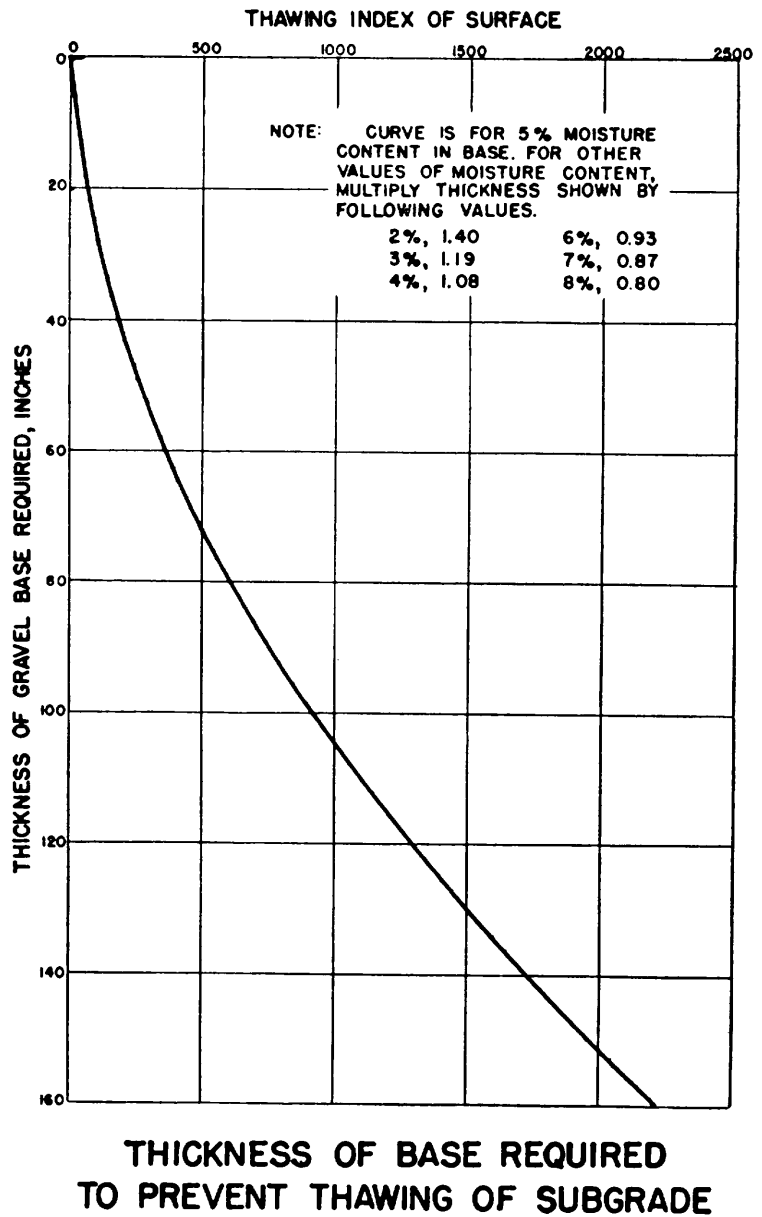


Figure 3.


GROUP	DESCRIPTION
F 1	GRAVELLY SOILS CONTAINING BETWEEN 3 AND 20 PER CENT FINER THAN 0.02 MM. BY WEIGHT.
F 2	SANDS CONTAINING BETWEEN 3 AND 15 PER CENT FINER THAN 0.02 MM. BY WEIGHT.
F 3	(a) GRAVELLY SOILS CONTAINING MORE THAN 20 PER CENT FINER THAN 0.02 MM. BY WEIGHT. (b) SANDS, EXCEPT VERY FINE SILTY SANDS, CONTAINING MORE THAN 15 PER CENT FINER THAN 0.02 MM. BY WEIGHT. (c) CLAYS WITH PLASTICITY INDEXES OF MORE THAN 12. (d) VARVED CLAYS EXISTING WITH UNIFORM SUBGRADE CONDITIONS.
F 4	(a) ALL SILTS INCLUDING SANDY SILTS. (b) VERY FINE SILTY SANDS CONTAINING MORE THAN 15 PER CENT FINER THAN 0.02 MM. BY WEIGHT. (c) CLAYS WITH PLASTICITY INDEXES OF LESS THAN 12. (d) VARVED CLAYS EXISTING WITH NON-UNIFORM SUBGRADE CONDITIONS.

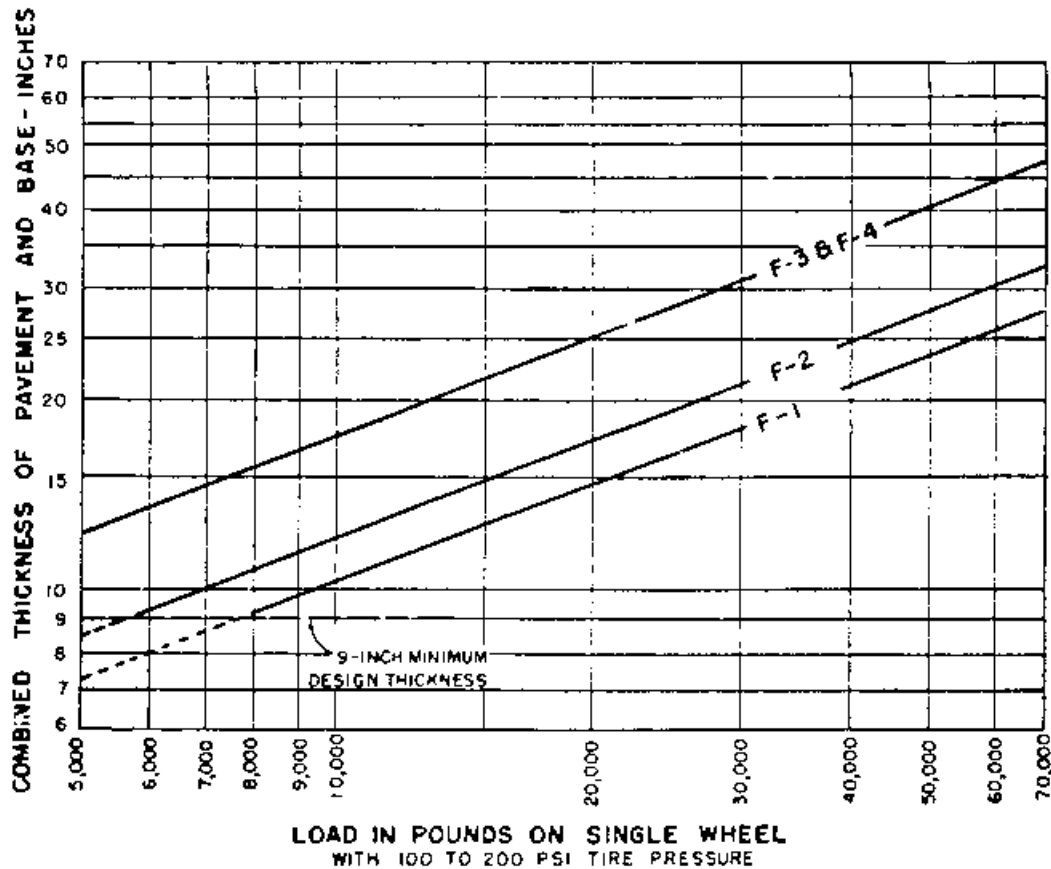

THE THICKNESS WILL BE REDUCED 10 PER CENT
FOR CENTRAL PORTION OF RUNWAYS (AREA BETWEEN 1000 FT. SECTION AT EACH END)
**FLEXIBLE PAVEMENT DESIGN CURVES FOR TAXIWAYS, ETC.
FOR
REDUCED STRENGTH OF SUBGRADE
ARCTIC AND SUBARCTIC REGIONS**

Figure 4.

GROUP	DESCRIPTION
F 1	GRAVELLY SOILS CONTAINING BETWEEN 3 AND 20 PER CENT FINER THAN 0.02 mm. BY WEIGHT.
F 2	SANDS CONTAINING BETWEEN 3 AND 15 PER CENT FINER THAN 0.02 mm. BY WEIGHT.
F 3	(a) GRAVELLY SOILS CONTAINING MORE THAN 20 PER CENT FINER THAN 0.02 mm. BY WEIGHT. (b) SANDS, EXCEPT VERY FINE SILTY SANDS, CONTAINING MORE THAN 15 PER CENT FINER THAN 0.02 mm. BY WEIGHT. (c) CLAYS WITH PLASTICITY INDEXES OF MORE THAN 12. (d) VARVED CLAYS EXISTING WITH UNIFORM SUBGRADE CONDITIONS.
F 4	(a) ALL SILTS INCLUDING SANDY SILTS. (b) VERY FINE SILTY SANDS CONTAINING MORE THAN 15 PER CENT FINER THAN 0.02 mm. BY WEIGHT. (c) CLAYS WITH PLASTICITY INDEXES OF LESS THAN 12. (d) VARVED CLAYS EXISTING WITH NON-UNIFORM SUBGRADE CONDITIONS.

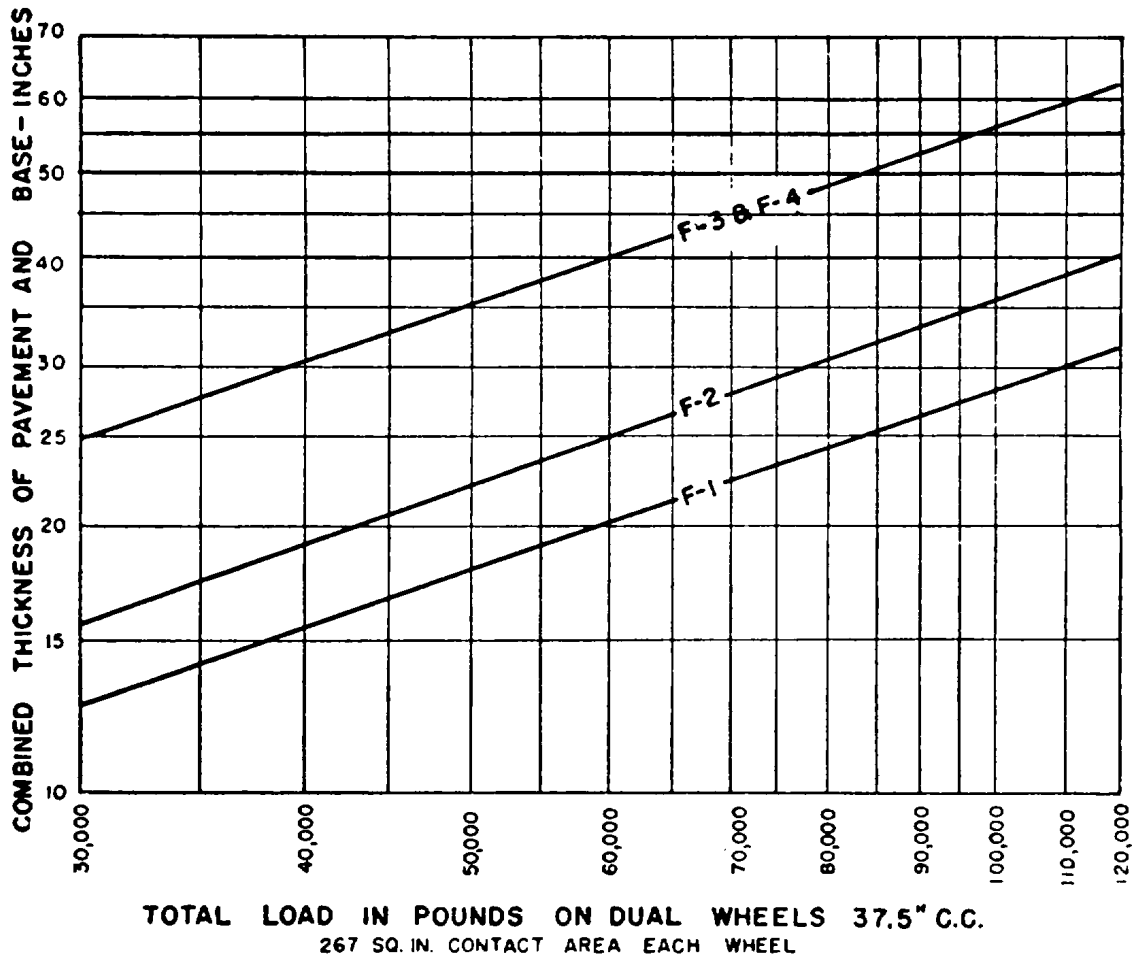


THE THICKNESS WILL BE REDUCED 10 PER CENT
FOR CENTRAL PORTION OF RUNWAYS (AREA BETWEEN 1000 FT. SECTION AT EACH END)

**FLEXIBLE PAVEMENT DESIGN CURVES FOR TAXIWAYS, ETC.
FOR
REDUCED STRENGTH OF SUBGRADE
ARCTIC AND SUBARCTIC REGIONS**

Figure 5.

GROUP	DESCRIPTION
F 1	GRAVELLY SOILS CONTAINING BETWEEN 3 AND 20 PER CENT FINER THAN 0.02 mm. BY WEIGHT.
F 2	SANDS CONTAINING BETWEEN 3 AND 15 PER CENT FINER THAN 0.02 mm. BY WEIGHT.
F 3	(a) GRAVELLY SOILS CONTAINING MORE THAN 20 PER CENT FINER THAN 0.02 mm. BY WEIGHT. (b) SANDS, EXCEPT VERY FINE SILTY SANDS, CONTAINING MORE THAN 15 PER CENT FINER THAN 0.02 mm. BY WEIGHT. (c) CLAYS WITH PLASTICITY INDEXES OF MORE THAN 12. (d) VARVED CLAYS EXISTING WITH UNIFORM SUBGRADE CONDITIONS.
F 4	(a) ALL SILTS INCLUDING SANDY SILTS. (b) VERY FINE SILTY SANDS CONTAINING MORE THAN 15 PER CENT FINER THAN 0.02 mm. BY WEIGHT. (c) CLAYS WITH PLASTICITY INDEXES OF LESS THAN 12. (d) VARVED CLAYS EXISTING WITH NON-UNIFORM SUBGRADE CONDITIONS.

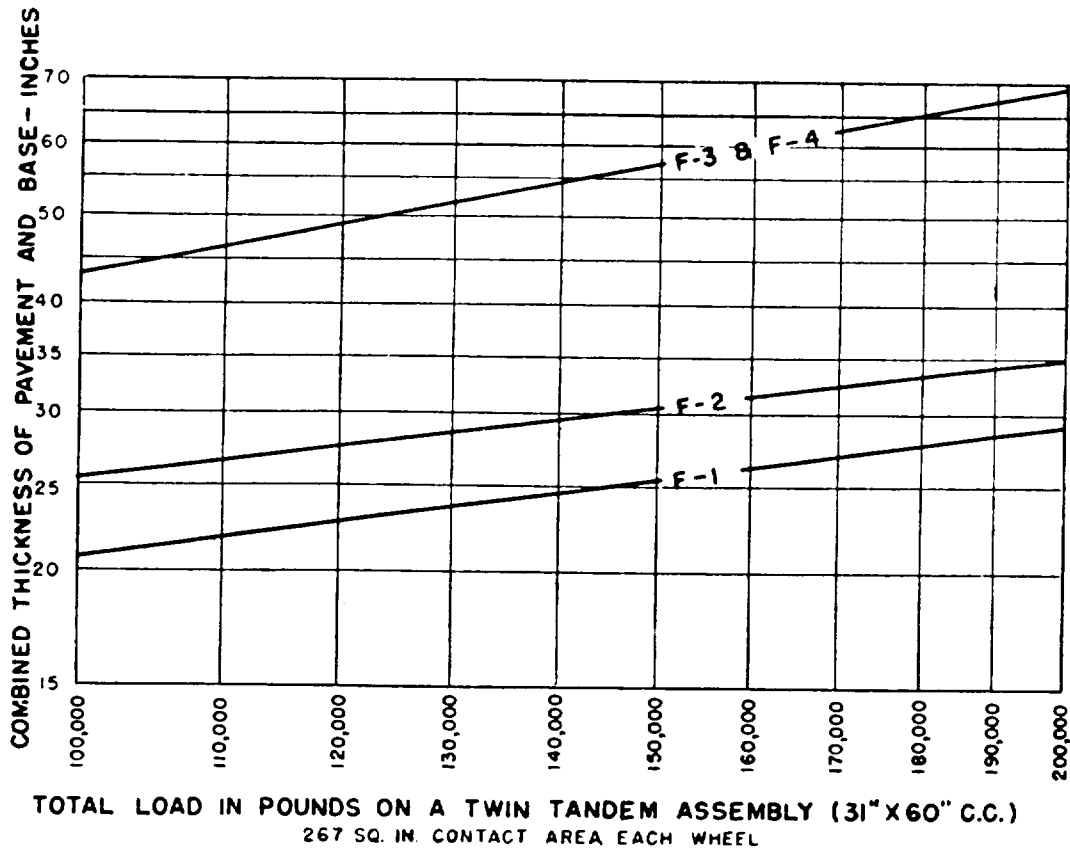


THE THICKNESS WILL BE REDUCED 10 PER CENT
FOR CENTRAL PORTION OF RUNWAYS (AREA BETWEEN 1000 FT. SECTION AT EACH END)

**FLEXIBLE PAVEMENT DESIGN CURVES FOR TAXIWAYS, ETC. -
FOR
REDUCED STRENGTH OF SUBGRADE
ARCTIC AND SUBARCTIC REGIONS**


Figure 6.

GROUP	DESCRIPTION
F 1	GRAVELLY SOILS CONTAINING BETWEEN 3 AND 20 PER CENT FINER THAN 0.02 mm. BY WEIGHT.
F 2	SANDS CONTAINING BETWEEN 3 AND 15 PER CENT FINER THAN 0.02 mm. BY WEIGHT.
F 3	(a) GRAVELLY SOILS CONTAINING MORE THAN 20 PER CENT FINER THAN 0.02 mm. BY WEIGHT. (b) SANDS, EXCEPT VERY FINE SILTY SANDS, CONTAINING MORE THAN 15 PER CENT FINER THAN 0.02 mm. BY WEIGHT. (c) CLAYS WITH PLASTICITY INDEXES OF MORE THAN 12. (d) VARVED CLAYS EXISTING WITH UNIFORM SUBGRADE CONDITIONS.
F 4	(a) ALL SILTS INCLUDING SANDY SILTS. (b) VERY FINE SILTY SANDS CONTAINING MORE THAN 15 PER CENT FINER THAN 0.02 mm. BY WEIGHT. (c) CLAYS WITH PLASTICITY INDEXES OF LESS THAN 12. (d) VARVED CLAYS EXISTING WITH NON-UNIFORM SUBGRADE CONDITIONS.

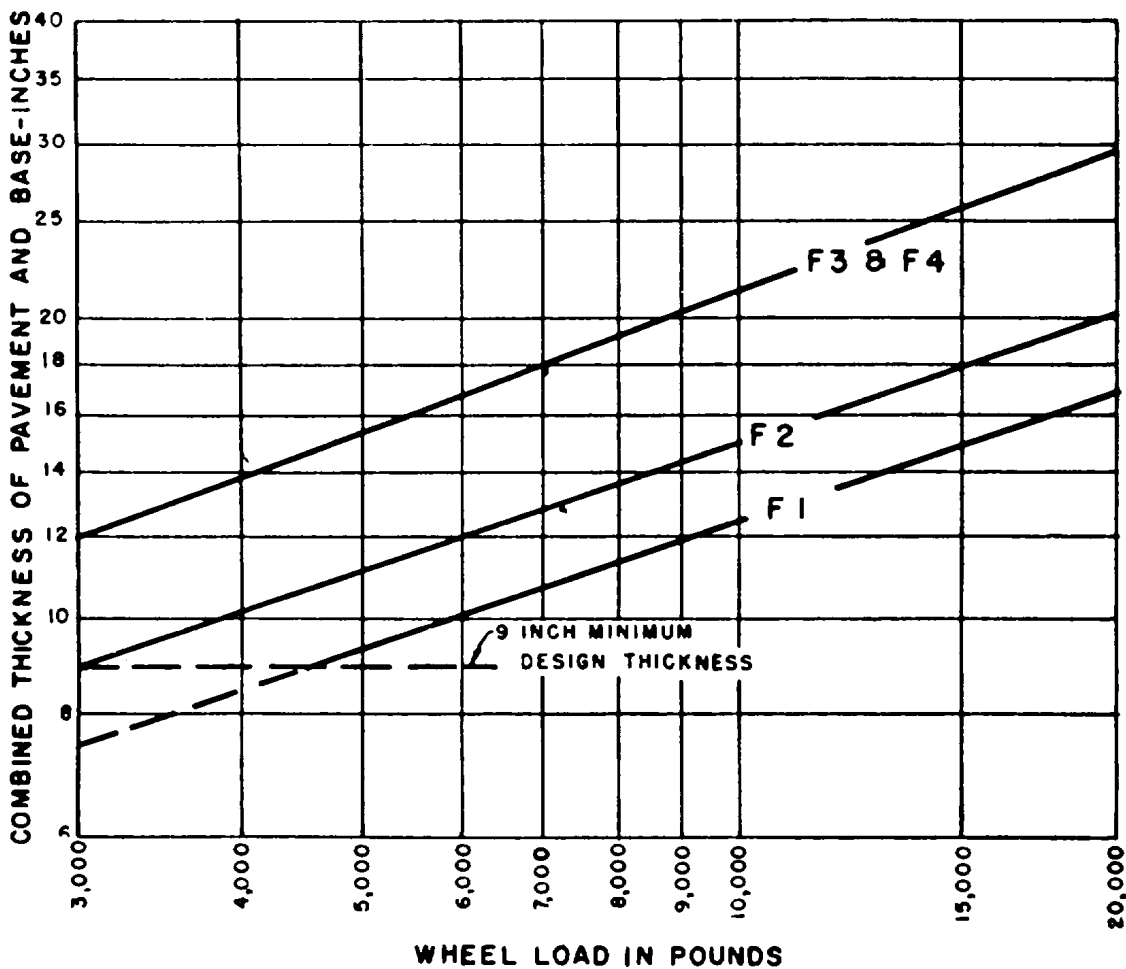

FLEXIBLE PAVEMENT DESIGN CURVES FOR HIGHWAYS, ETC.
FOR
REDUCED STRENGTH OF SUBGRADE
ARCTIC AND SUBARCTIC REGIONS


THAWING INDEX OF SURFACE, DEGREE-DAYS (F)

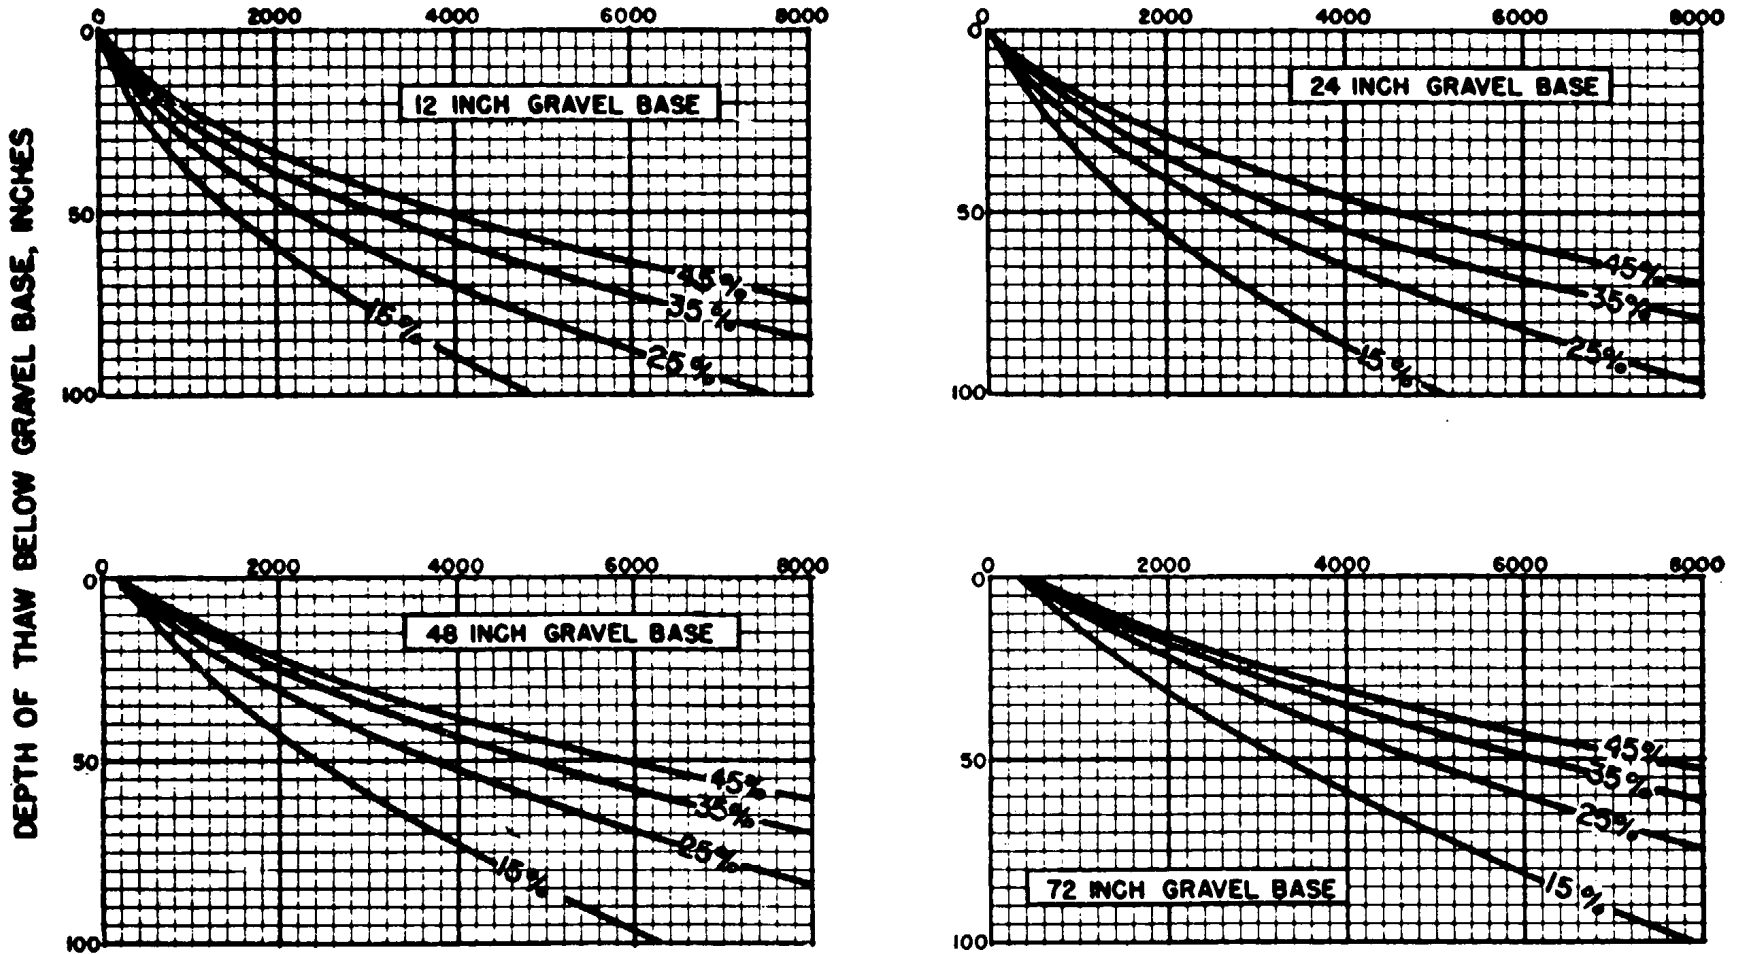

**CURVES FOR DETERMINATION OF DEPTH OF THAW
BENEATH PAVEMENTS WITH GRAVEL BASES**

NOTE: VALUES ON CURVES ARE MOISTURE CONTENT OF FROST-SUSCEPTIBLE SUBGRADE
PAVEMENT SURFACE EITHER BITUMINOUS OR CONCRETE.
DEPTHS ARE FROM TOP OF SUBGRADE.

Figure 8.

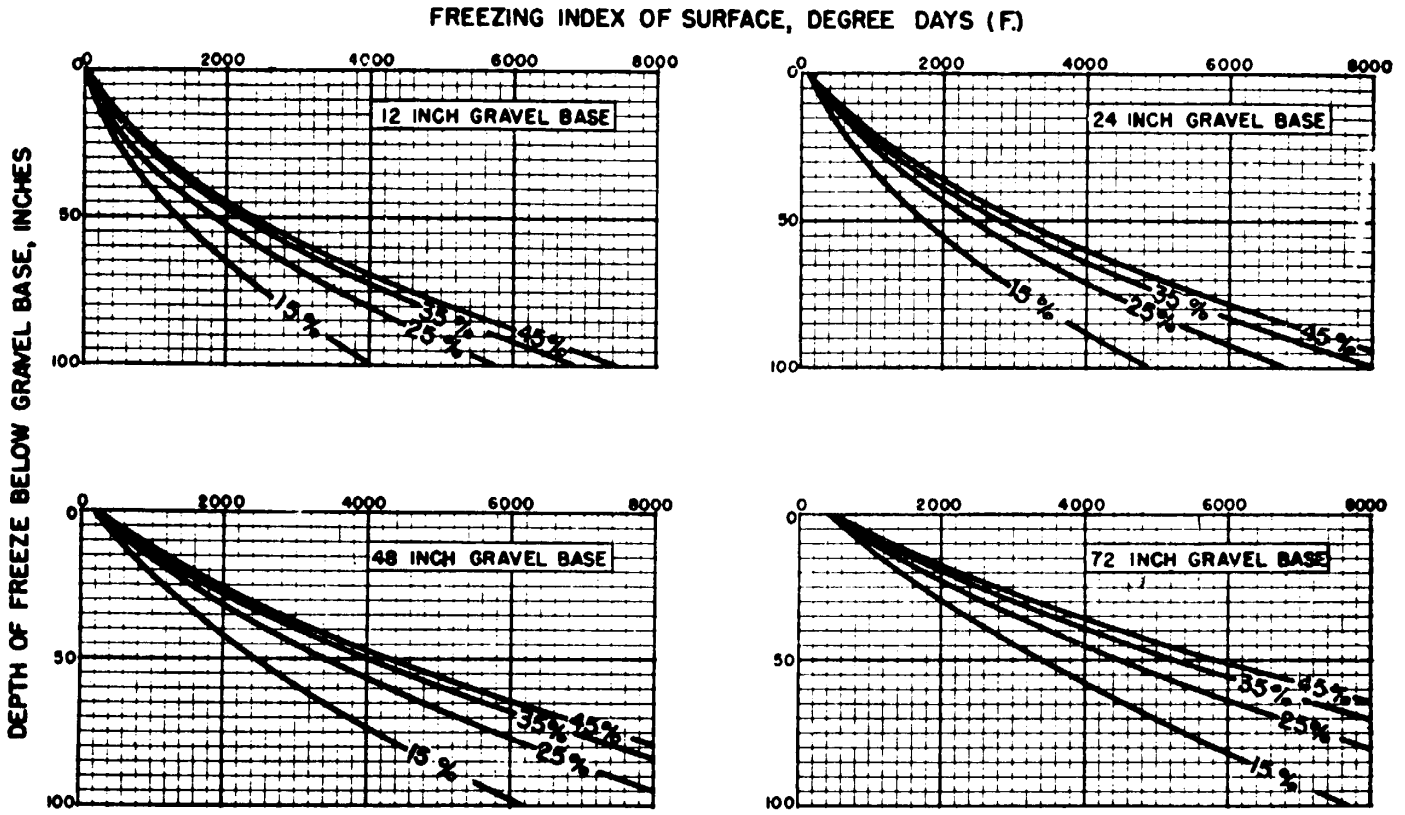


**CURVES FOR DETERMINATION OF DEPTH OF FREEZE
BENEATH PAVEMENTS WITH GRAVEL BASES**

NOTE: VALUES ON CURVES ARE MOISTURE CONTENT OF FROST-SUSCEPTABLE SUBGRADE
PAVEMENT SURFACE EITHER BITUMINOUS OR CONCRETE.
DEPTHS ARE FROM TOP OF SUBGRADE.

Figure 9.
20

GROUP	DESCRIPTION
F 1	GRAVELLY SOILS CONTAINING BETWEEN 3 AND 20 PER CENT FINER THAN 0.02 mm. BY WEIGHT.
F 2	SANDS CONTAINING BETWEEN 3 AND 15 PER CENT FINER THAN 0.02 mm. BY WEIGHT.
F 3	(a) GRAVELLY SOILS CONTAINING MORE THAN 20 PER CENT FINER THAN 0.02 mm. BY WEIGHT. (b) SANDS, EXCEPT VERY FINE SILTY SANDS, CONTAINING MORE THAN 15 PER CENT FINER THAN 0.02 mm. BY WEIGHT. (c) CLAYS WITH PLASTICITY INDEXES OF MORE THAN 12. (d) VARVED CLAYS EXISTING WITH UNIFORM SUBGRADE CONDITIONS.
F 4	(a) ALL SILTS INCLUDING SANDY SILTS. (b) VERY FINE SILTY SANDS CONTAINING MORE THAN 15 PER CENT FINER THAN 0.02 mm BY WEIGHT (c) CLAYS WITH PLASTICITY INDEXES OF LESS THAN 12 (d) VARVED CLAYS EXISTING WITH NON-UNIFORM SUBGRADE CONDITIONS.

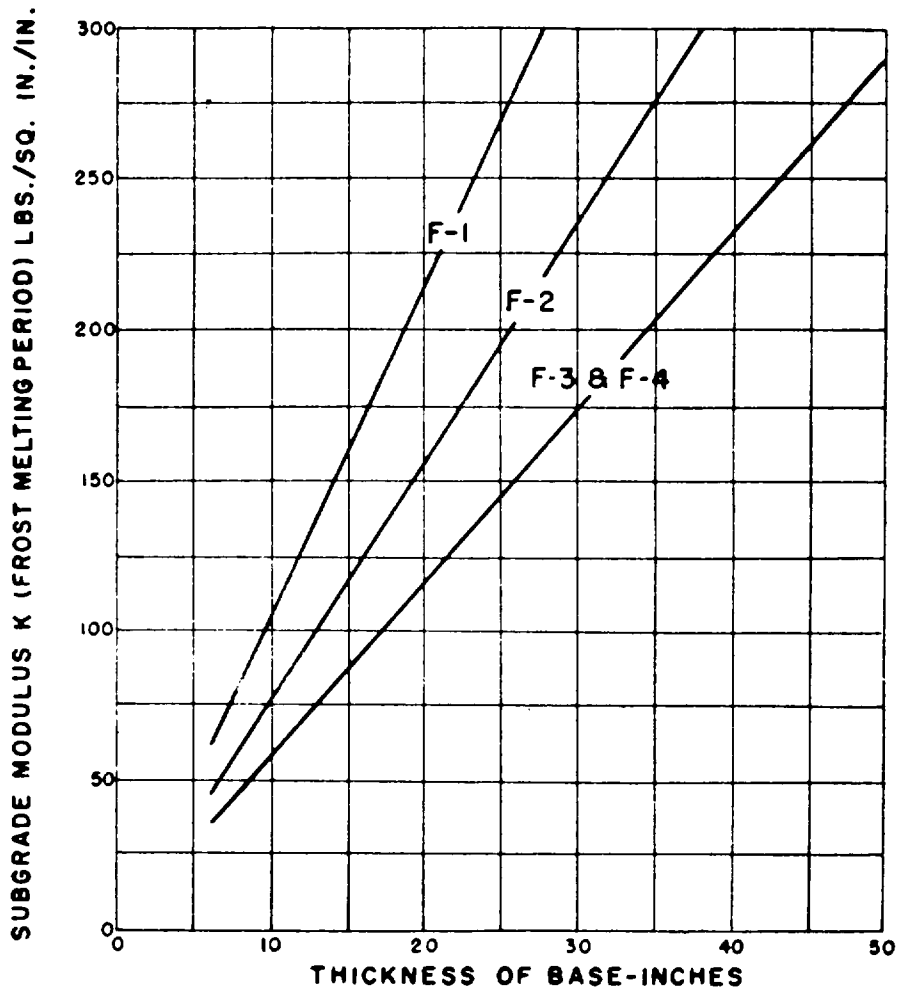

**RIGID PAVEMENT SUBGRADE MODULUS CURVES
FOR
REDUCED STRENGTH OF SUBGRADE
ARCTIC AND SUBARCTIC REGIONS**

Figure 10.

PIN: 024917-000